

Concrete Made for Energy Conservation Using Recycled Rubber Aggregates

Moayyad Al-Nasra¹, Zeljko Torbica¹

¹ LCN College of Engineering and Sciences; West Virginia University Institute of Technology, Montgomery, WV 25136

ABSTRACT: Recycling material is a key solution in achieving sustainability that will enable the earth to continue to support human life. The potential use of recycled materials in construction has been explored previously. Several recycled materials were used in concrete for the purpose of improving the quality of concrete in terms of its performance under loads. Other recycled materials were used in concrete mainly for the purpose of saving energy as well as providing unconventional solutions to particular environmental problems. In this study, recycled aggregates made from used tires from landfills were used as recycled material in concrete production. The shape, size and gradation of these recycled aggregates are designed for better bonding with the surrounding concrete paste. The new modified concrete showed real possibility of using recycled tires in concrete and concrete block. The new modified concrete can be used as structural and non-structural components in concrete structures. This research aimed to evaluate the feasibility of using rubber in the concrete mix design that also includes mineral aggregates, water and Portland cement. Samples were created using ¼ in to 1.5 in. rubber aggregates with holes drilled at their center. Several samples were prepared and tested in the lab. The results are presented and discussed in this study. The results showed that the strength of concrete decreases with the increase of the amount of rubber aggregates used in the mix. This study also showed that the thermal conductivity will be improved by the increase amount of recycled aggregates used in the mix by reducing the heat transfer and increasing the thermal resistance of the concrete.

KEYWORDS: Recycled aggregate, Rubber aggregates, Rubberized concrete, Thermal conductivity, Energy conservation, Mechanical properties

I. INTRODUCTION

For many years, cities have been faced with increasing problems with the disposal of recycled materials, such as rubber, glass, and plastics. In 2010, the world's rubber consumption reached nearly 24.9 million tons (IRSG 2012). In the U.S. alone 3.9 million tons of scrap tires are produced annually from that 1.36 million tons are recycled and 2.54 million tons are burned or land filled (Department of Energy and Environmental Protection). Despite the large market for scrap tires, roughly a quarter of all scrap tires end up in landfills each year numbering to approximately 27 million tires or roughly 6 million tons annually making up over 12% of all solid waste (US EPA, 2003). Due to the cross-links between the rubber polymer chains, numerous additives, and stabilizers within its structure, the rubber is extremely resistant to natural degradation making it troublesome for landfill storage (Stevenson et al., 2008). When these materials are sent to landfills they become expensive to dispose of, decrease the number of landfills, and become a hazard towards the environment (Koren 2003). Fig. 1 shows typical site of discarded tires. As stated by the Rubber Manufacturers Association (RMA), rubber tire piles can become a breeding place for disease carrying mosquitoes and can catch fire through arson, or accident, that are difficult to put out, produce heavy smoke, and toxic runoff into waterways (R.M.A. 2011). Fig. 2 shows burning of used tires that can be considered as an environmental critical issue. Based on this information, crumb rubber use in concrete and pavements provides an environmentally sustainable method for disposing the millions of tires generated annually.



Figure 1: Discarded tires.



Figure 2: Burning used rubber tires.

Crumb rubber is a term given to recycled rubber produced from scrap tires. Production of crumb rubber consists of removing steel and fluff then using a granulator and/or cracker mill, with the aid of cryogenics or mechanical means, to reduce the size of the tire particles. The rubber particles are then sized by passing them through a set of sieves. The methods for grinding down the tires are either using ambient or cryogenic means. The goal of these processes is to reduce the size of the rubber into a fine powder of particle sizes smaller than 2.0 mm in diameter (RMA, 2011). For pavements, the modification of asphalt mixture with rubber is classified into three different methods; dry process which uses crumb rubber as an aggregate substitute, wet process with agitation in which large particles (particles not passing No. 50 Sieve) are blended with the binder while applying agitation during mixing to keep crumb rubber particles uniformly distributed, and wet process with no agitation in which small particles (passing No. 50 Sieve) are blended with asphalt binder with no agitation. Yesilata, Isiker, and Turgut (Yesilata, et. 2009) investigated the thermal enhancement in concretes by adding shredded waste polyethylene bottles and automobile tire. These materials are obtained from the environment and prove to be little to no cost. The results revealed a significant amount of reduce heat loss. However, the improved thermal insulation varies with the amount added material and the geometry of the shredded pieces.

The focus of this research work is to investigate the thermal conductivity of concrete mixed with rubber aggregates of designed shapes made from rubber waste particles replacing 10% to 20% of the regular aggregates. The experimental work uses pieces of automobile tire to develop a lightweight concrete material with lower thermal conductivity. The rubber pieces are cut into semi cubical shapes with holes in the center to increase the bonding strength with the concrete paste as shown in Fig. 3. These rubber pieces are then chemically treated with sodium hydroxide (NaOH) to enhance the bonding strength as shown in Fig. 4. The rubber aggregates were soaked in a solution of sodium hydroxide then cleaned and dried before using them in the concrete mix. The use of rubber aggregates will allow reduction of heat transfer into buildings and decrease the energy consumption. The thermal tests were performed by using the Hot Box method. In addition to thermal properties, the research investigates the mechanical properties of the concrete mixed with these specifically designed particles including compression and indirect tension tests.

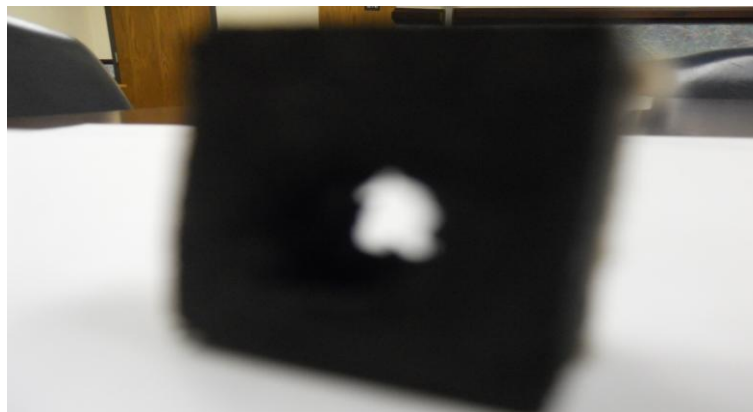


Figure 3: Typical rubber aggregate used in this study



Figure 4: Rubber aggregates conditioned by sodium hydroxide

II. BACKGROUND

Sustainable materials should be used by the construction industry to compensate for the increasing waste problem. Automobile tires have been used in several rubber products, production of electricity, or fuel. Portland cement is the principle binder in concrete and is a major contributor to greenhouse gas emissions and the Portland cement industry is one of the two largest carbon dioxide producers (Mehta 2004). Khatib and Bayomy (Khatib, et. 1999) investigated rubberized Portland cement concrete using fine crumb rubber and course tire chips. The rubber concrete mixes were tested for compressive and flexural strength in accordance to ASTM standards. Their results showed rubber contents should not exceed 20 percent of the total aggregate volume and may be suitable for nonstructural purposes such as lightweight concrete walls, building facades, and architectural units. Frankowski (Frankowski 1995) investigated rubber crumb reinforced cement concrete for structures. His results showed that rubber crumb reinforced cement concrete provided resistance to cracking, increased the resistance to acid rain, lowered the weight, improved shock wave absorption, lowered heat conductivity and improved the acoustical environment.

A solution to reduce waste and large quantities of industrial by-products is to use recycled concrete aggregate (RCA) from construction and demolition projects, rubber tires from landfills, and fly ash from burning coal into a production of concrete. Yet, most concrete structures are designed to last up to 50 years (Mehta 2004). Yilmaz and Degirmenci (Yilmaz, et. 2009) investigated the use of rubber and fly ash waste in Portland cement as construction material. They found the compressive strength decreased with the increase of rubber content and would increase with the increase of fly ash. They also proved tire rubber particles have sufficient strength for masonry applications. Toutanji (Toutanji 1996) investigated the use of rubber tire particles in concrete to replace mineral aggregates. He tested for compressive and flexural strength and revealed that high toughness was displayed along with a reduction in compressive and flexural strength with the increase of rubber added. Biel and Lee (Biel, et. 1996) investigated Portland cement and magnesium oxychloride cement as binders for concretes with rubber aggregate. The concrete samples were tested for both compressive and splitting tensile strengths to determine if the cement with tire rubber would improve concrete properties. With 25 percent of rubber by volume, both Portland and magnesium oxychloride cement concretes lost 90 percent of their compressive strength. Tensile strength, Portland cement concrete retained 20 percent and magnesium oxychloride retained 35 percent.

Another sustainable aspect is energy consumption and energy use in buildings. Approximately 25-30 percent of the total energy that is consumed in the world today is used in buildings. Whereas in commercial and residential buildings, around 80 percent of total energy consumed is used for space heating and cooling (Yesilata, et. 2010). Therefore, enhance thermal protection is key to acquiring a reasonable energy consumption level in construction of buildings. Asan and Sancaktar (Asan, et. 1998) investigate the thermo physical properties and wall thickness of buildings on time lag and decrement factor. They solved for heat conduction under convection boundary conditions and found that time lag and decrement was affected by thermo physical properties. Papadopoulos and Giama (Papadopoulos, et. 2007) investigated the environmental performance of thermal insulation materials and its impact on buildings. They show that contemporary insulation materials achieve thermal conductivity values of less than 0.04W. Their results obtained were used to set environmental condition indicators on the ISO 14031 standard and met the Environmental Performance Evaluation.

The production of thermal insulation materials is a key solution to solve the greater problem of recycling industrial and domestic waste, and energy consumption in construction. Sukontasukkul (Sukontasukkul 2009) studied the thermal and sound properties of crumb rubber concrete panels. Replacing 10%, 20%, and 30% of crumb rubber in concrete, the results indicated a lighter, higher sound absorption, and lower heat transfer properties than the conventional concrete panel. Phan and Carino (Phan, et. 2000) investigated fire performance in high strength concrete(HSC) and normal strength concrete(NSC). The differences are most pronounced in the temperature range 20 degrees Celsius and 400 degrees Celsius in which their results conclude recommended research needs. In their work, they used rubber waste particles and fly ash as raw materials, to develop a lightweight construction material with lower thermal conductivity. This will allow reduction of heat transfer into buildings and decrease the energy consumption.

III. THERMAL CONDUCTIVITY TEST

Benazzouk, Douzane, Mezreb, Laidoudi, and Queneudec (Benazzouk, et. 2008) studied thermal conductivity of cement composites containing rubber waste particles of 10 percent to 50 percent with 10 percent increment by volume. For their experiment, they used shredded automobile tire and cement with Standard NF P 15-301. Using the transient plane source (TPS) method, they created a three-dimensional heat flow inside the sample. A disk shaped TPS element was in between two cubic samples, all pressed together by chucking device

to ensure contact between the TPS sensor and the sample. A constant pulse was passed through the heating element. The temperature was then recorded by recording the voltage increase. The duration of the experiment lasted 360 seconds and revealed that the addition of rubber improved the thermal conductivity. The results were portrayed in a chart that showed a decrease of about 60% thermal conductivity using a sample containing 50 percent rubber particle.

Yesilata, Bulut, and Turgut (Yesilata, et. 2010) studied the thermal behavior of a building structure using rubberized concrete exterior walls. They constructed two model rooms, one whose exterior walls were fully made with rubberized concrete and the other room fully surrounded by ordinary concretes. Long term thermal behaviors were investigated and compared under real atmospheric conditions. The indoor temperatures of the rubberized concrete walls were lowered which in turn affected the outdoor conditions. Their results show that rubberized concrete improves thermal protection and is a cost effective solution. Therefore, enhance thermal protection should be incorporated in the new construction and rehabilitated buildings to reach a desired energy consumption.

Yesilata, Isiker, and Turgut (Yesilata, et. 2009) investigated the thermal enhancement in concrete by adding shredded waste polyethylene bottles and automobile tire. Thermal tests were performed by using the dynamic adiabatic-box technique to determine the effectiveness of the thermal transmittances of the concrete samples. The outer and bottom walls are heavily insulated to minimize the heat loss of the samples to the surroundings. The brick samples create the top wall of the box. The box is in a surrounding cool room as the bottom of the box is filled with water that is heated by a heater. Since major part of heat is transferred through the surface of the sample, the cooling rate of water became a considerable measurement of the sample's thermal transmittance. The results revealed a significant amount of reduce heat loss. However, the improved thermal insulation varies with the amount added material and the geometry of the shredded pieces.

Turgut and Yesilata (Turgut, et. 2008) investigated the thermal performances of rubberized brick. They examine rubber added brick in buildings to produce low cost and lightweight brick with improved thermal resistance. For the experiment, they too used the dynamic adiabatic-box technique as discussed previously by Yesilata, Isiker, and Turgut (Yesilata, et. 2009). Their results revealed that the bricks to have high energy absorption capacity. They also concluded that the thermal insulation performance is improved by introducing various amounts of crumb rubber into mixes.

IV. MATERIALS

The materials used in this experiment included Portland cement, sand, aggregates, rubber aggregates, and water. For this experiment, separate batches were created at different amounts of rubber aggregates used per batch. The focus was on 0 percent, 10 percent and 20 percent of rubber aggregates replacement of the mineral aggregates. The mix design remained the same but portion of the mineral aggregates were replaced by rubber aggregates at a rate of 0 percent to 20 percent. Table 1 shows the mix design used in this study.

Table 1: Standard concrete ingredients used in this study

| Material | Weight (kg) | Weight (N) |
|------------------------|-------------|------------|
| Water | 6.3 | 61.8 |
| Portland cement type I | 14.0 | 137.3 |
| Coarse aggregates | 39.0 | 382.5 |
| Fine aggregates | 27.9 | 264.8 |

V. CONCRETE STRENGTH RESULTS

Several concrete cylinders were prepared to study the effect of using rubber tires as a partial replacement of coarse aggregates. Fig. 5 shows splitting test of one of the tested samples. Fig. 6 and Fig. 7 show that the strength of concrete is reduced substantially by the increase of the amount of rubber used. Standard concrete cylinders were used (6 inches by 12 inches). Several batches were prepared and tested. The water cement ration was taken to be 0.45, and the max mineral aggregate size is ¾ inch.



Figure 5: Splitting test

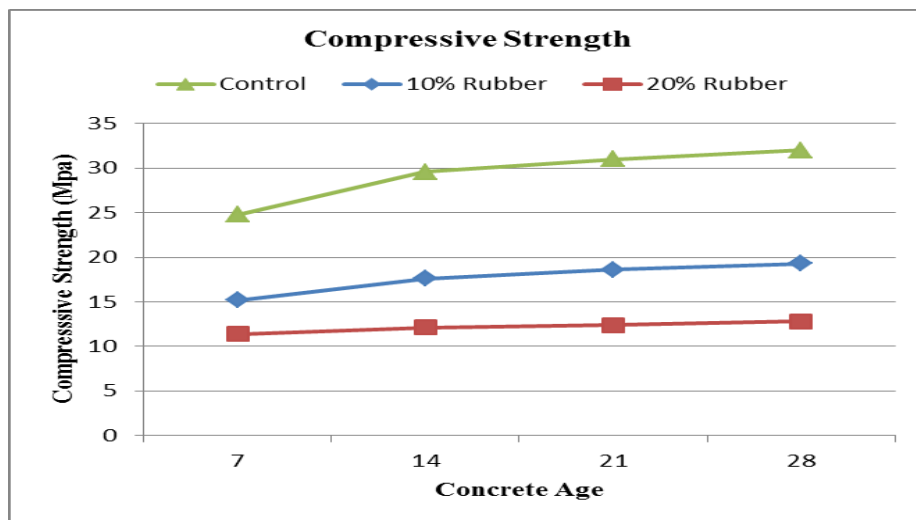


Figure 6: Concrete compressive strength at different rubber amounts

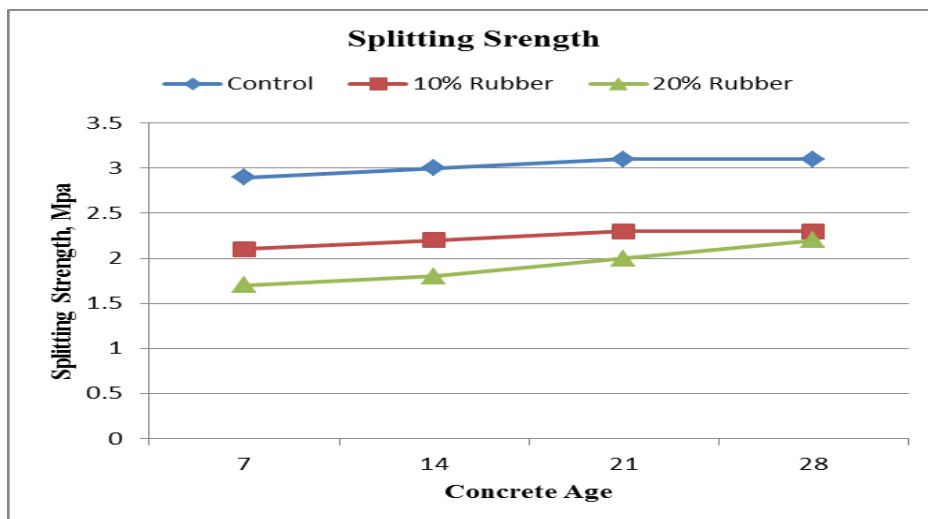


Figure 7: Concrete splitting strength at different rubber amounts

Adding rubber tires pieces in concrete can improve some of the concrete properties, including insulation, unit weight, and thermal conductivity. Other properties needed to be studied in more depth. The compressive strength of concrete decreases with the increase of the amount of rubber used in the concrete mix. Studies showed that the maximum amount of rubber to be used in the concrete mix should be less than 20%. Other studies showed that the concrete strength improved substantially by conditioning the rubber before the mixing process. Sodium Hydroxide (NaOH) is proven to be effective in conditioning the tire rubber by improving the bonding strength between the rubber particles and the concrete paste.

VI. THERMAL PROPERTIES OF CONCRETE WITH RUBBER AGGREGATES

As Yesilata and Bulut concluded from their experimental study, addition of rubber pieces lowers indoor and outdoor temperature variations and the effect of outdoor conditions (Yesilata, et. 2010). They also revealed an 11 percent improvement in thermal protection of a rubberized concrete wall that proves cost effective for people of low income and/or living in rural areas. Yesilata and Islker also concluded with the addition of selected materials, such as fly ash and rubber into the concrete mix, the thermal insulation performance will be significantly improve (Yesilata, et. 2009). The degree of thermal insulation improvement was based on the geometry of the shredded rubber and the amount.

Fig. 8 shows the design of the hot box used in this study. The concrete slab sample of 2 inches (5 cm) thick is placed in the center of the hot box. A total of eight thermal sensors were used to measure the temperature at 5 minutes interval. The difference between the temperature reading in the compartment of the heat source and the temperature reading of the upper compartment is recorded. Three different slab samples were studied; plain concrete sample with no rubber aggregates (0%), 10% rubber aggregates replacement and 20% rubber aggregate replacement.

The rate of heat transfer (Q) is defined as

$$Q=kA(T1-T2)/t$$

Where

Q = Heat transfer rate, W

k = Heat transfer coefficient, W/m/°C

A = Area m²

(T1-T2) = Temperature difference, °C

t = Concrete slab thickness, m

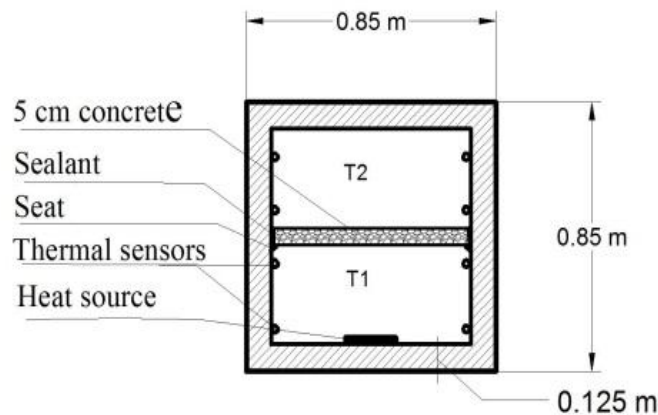


Figure 8: Hot box design

Fig. 9 shows the results of the heat transfer experiment using the hot box shown in Fig. 8. The temperature difference reduces with the increase in the amount of rubber aggregates used in the concrete mix. There is about 10 percent and 24 percent reduction in temperature difference for the 10% rubber sample and the 20 rubber sample respectively.

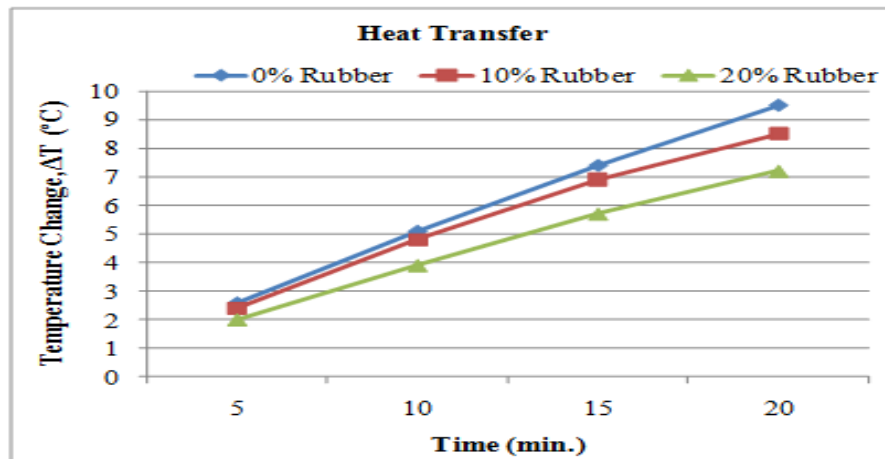


Figure 9: Heat transfer results

VII. CONCLUSION

This study proved that there is a great potential for the used rubber tires to be used effectively in concrete. Even though, the addition of rubber aggregates decreases the concrete compressive and tensile strength, there are several properties that can be improved by adding rubber aggregate to the concrete. The thermal conductivity of concrete mixed with rubber aggregate will be reduced proportionally with the increase of the amount rubber aggregates used in the mix by increasing the thermal resistance. This abundant waste material exists in the environment and can be obtained with almost no cost. The use of rubber in concrete is an excellent choice for attaining sustainability, a cleaner environment, and a reduction in insulation cost.

REFERENCES

- [1]. Asan, H. and Sancaktar, Y. (1998). "Effects of Wall's thermophysical properties on time lag and decrement factor." *Energy and Buildings Journal*, Elsevier, Vol. 28, No. (2), page 159-166, DOI: [http://dx.doi.org/10.1016/S0378-7788\(98\)00007-3](http://dx.doi.org/10.1016/S0378-7788(98)00007-3).
- [2]. Benazzouk, A., Douzane, O., et al. (2008). "Thermal conductivity of cement composites containing rubber waste particles: Experimental study and modelling." *Construction and Building Materials Journal* Elsevier, Vol. 22 No. (4) pages 573-579, www.sciencedirect.com
- [3]. Biel, T. D. and Lee, H. (1996). "Magnesium oxychloride cement concrete with recycled tire rubber." *Transportation Research Record: Journal of the Transportation Research Board* No. 1561, Transportation Research Board, Washington DC, pages 6-12.
- [4]. Frankowski, R. (1995). Rubber-crumb-reinforced cement concrete, US Patents # 5,391,226.
- [5]. Hernandezolivas, F. (2004). "Fire performance of recycled rubber-filled high-strength concrete." *Cement and Concrete Research* Vol. 34 No. (1) pages: 109-117, www.sciencedirect.com
- [6]. International Rubber Study Group (IRSG). 2012. Statistical summary of world rubber situation. Available at <http://www.rubberstudy.com/documents/WebSiteData.pdf>, accessed March 15, 2012.
- [7]. Khatib, Z. K. and Bayomy, F. M. (1999). "Rubberized Portland Cement Concrete." *Journal of Materials in Civil Engineering* Elsevier, Vol. 11 No. (3), pages 206-213, [http://dx.doi.org/10.1061/\(ASCE\)0899-1561\(1999\)11:3\(206\)](http://dx.doi.org/10.1061/(ASCE)0899-1561(1999)11:3(206)).
- [8]. Koren, H. and Bisesi, M.S. (2002). *Handbook of Environmental Health* (4th ed.) Vol. II. Pollutant Interactions in Air, Water and Soil. CRC Press (Taylor-Francis Group) Boca Rotan, FL <http://cph.osu.edu/people/mbisesi#sthash.kYXZOUNO.dpuf>
- [9]. Mehta, P. K. (2004). "High-Performance, High-Volume Fly Ash Concrete for Sustainable Development," *Proceedings of the International Workshop on Sustainable Development & Concrete Technology*, pp. 3-14; May 2004.
- [10]. NETZSCH (2009). "Differential Scanning Calorimetry/ Differential Thermal Analysis." from www.netzsch-thermal-analysis.com.
- [11]. Papadopoulos, A. and Giama, E. (2007). "Environmental performance evaluation of thermal insulation materials and its impact on the building." *Building and environment*, Vol. 42 No. (5) pages 2178-2187.
- [12]. Phan, L. T. and Carino, N. J. (2000). Fire performance of high strength concrete: research needs Advanced Technology in Structural Engineering. ASCE/SEI Structures Congress 2000. Proceedings. May 8-10, 2000, Philadelphia, PA, Elgaaly, M., Editor(s), 2000.
- [13]. R.M.A., R. (2011). "Scrap Tires and the Environment." Retrieved 07/15/2011, from <http://www.rma.org>.
- [14]. Sukontasukkul, P. (2009). "Use of crumb rubber to improve thermal and sound properties of pre-cast concrete panel." *Construction & Building Materials*, Vol. 23 No. (2), pages 1084-1092.
- [15]. Stevenson, K., Stallwood, B., & Hart, A. G. (2000). "Tire Rubber Recycling and Bioremediation: A Review," *Bioremediation Journal*, Vol. 12 No. (1), pages 1-11.
- [16]. Toutanji, H. A. (1996). "The Use of Rubber Tire Particles in Concrete.", *Cement and Concrete Composites*, Vol. 18, No. 2, pp. 135-139. doi:10.1016/0958-9465(95)00010-0
- [17]. Turgut, P. and Yesilata, B. (2008). "Physico-mechanical and thermal performances of newly developed rubber-added bricks." *Energy and Buildings* Vol. 40 No. (5), pages 679-688, www.sciencedirect.com.
- [18]. Yesilata, B., Bulut, H. (2011). "Experimental study on thermal behavior of a building structure using rubberized exterior-walls." *Elsevier, Energy and Buildings*, Vol. 43, Issues 2-3, pages 393-399
- [19]. Yesilata, B., IsIker, Y., Turgut, P. (2009). "Thermal insulation enhancement in concretes by adding waste PET and rubber pieces," *Elsevier, Construction and Building Materials*, Vol. 23 No. (5), pages 1878-1882.
- [20]. Yilmaz, A. and Degirmenci, N. (2009). "Possibility of using waste tire rubber and fly ash with Portland cement as construction materials." *Waste Management*, Vol. 29 No. (5), pages 1541-1546.